

1 **Microencapsulation of a synbiotic into PLGA/alginate**
2 **multiparticulate gels**

3
4 **Michael T. Cook^a, George Tzortzis^b, Dimitris Charalampopoulos^{c*}, Vitaliy V. Khutoryanskiy^{a*}**

5 *^aSchool of Pharmacy, University of Reading, Reading, RG6 6AD, United Kingdom*

6 *^bClasado Research Services Ltd, Science and Technology Centre, University of Reading, Earley*
7 *Gate, Whiteknights Road, Reading, RG6 6BZ, United Kingdom*

8 *^cDepartment of Food and Nutritional Sciences, University of Reading, Reading, RG6 6AD,*
9 *United Kingdom*

10 **Corresponding authors at:*

11 *Vitaliy Khutoryanskiy: School of Pharmacy, University of Reading, Reading, RG6 6AD, United*
12 *Kingdom*

13 *Dimitris Charalampopoulos: Food and Nutritional Sciences, University of Reading, Reading,*
14 *RG6 6AD, United Kingdom*

15
16 *E-mail: V.Khutoryanskiy@reading.ac.uk*

17 *Tel: +44 (0) 118 378 6119*

18
19 **Keywords:** prebiotic, probiotic, encapsulation, GOS, galacto-oligosaccharides, bifidobacterium.
20
21
22
23
24

Abstract

Probiotic bacteria have gained popularity as a defence against disorders of the bowel. However, the acid sensitivity of these cells results in a loss of viability during gastric passage and, consequently, a loss of efficacy. Probiotic treatment can be supplemented using 'prebiotics', which are carbohydrates fermented specifically by probiotic cells in the body. This combination of probiotic and prebiotic is termed a 'synbiotic'. Within this article a multiparticulate dosage form has been developed, consisting of poly(D,L-lactic-co-glycolic acid) (PLGA) microcapsules containing prebiotic Bimuno™ incorporated into an alginate-chitosan matrix containing probiotic *Bifidobacterium breve*. The aim of this multiparticulate was that, *in vivo*, the probiotic would be protected against gastric acid and the release of the prebiotic would occur in the distal colon. After microscopic investigation, this synbiotic multiparticulate was shown to control the release of the prebiotic during *in vitro* gastrointestinal transit, with the release of galacto-oligosaccharides (GOS) initially occurred over 6 h, but with a triphasic release pattern giving further release over 288 h. Encapsulation of *B.breve* in multiparticulates resulted in a survival of 8.0 ± 0.3 log CFU/mL cells in acid, an improvement over alginate-chitosan microencapsulation of 1.4 log CFU/mL. This was attributed to increased hydrophobicity by the incorporation of PLGA particles.

Abbreviations: DCM, dichloromethane; FITC, fluorescein isothiocyanate; GI, gastrointestinal; GOS, galacto-oligosaccharides; IL-6, interleukin-6; PBS, phosphate-buffered saline; polydispersity index, PDI; PLGA, poly(D,L-lactic-co-glycolic acid); TNF- α , tumor necrosis factor α ; WC, Wilkins-Chalgren

1.0 Introduction

Probiotic bacteria have attracted interest due to their potential to alleviate some specific conditions of the bowel when administered orally (Rembacken et al., 1999). The intention of taking these cells orally is to modify the balance of the indigenous gut microflora in favour of strains which can exert some positive biological action (Fuller, 1991). These biological actions are numerous, and sometimes poorly understood. Examples of probiotic action include: the modulation of immune response, competition with pathogens and the production of antimicrobial compounds (Ng et al., 2009). Research suggests that these cells are most effective whilst live (or 'viable'), and passage through the stomach often results in cell death, lowering the efficacy of an administration. Thus, research has focused on methods to improve cell survival in the stomach, and, as a result, improve the efficacy of a probiotic (Cook et al., 2012). Commonly, microencapsulation, which involves the entrapment of the probiotic cells into polymeric materials, is used to achieve this aim. Research has traditionally focussed on the use of polysaccharides, such alginate (Chavarri et al., 2010; Cook et al., 2011; Cook et al., 2013; Mokarram et al., 2009), xanthan gum (Ding and Shah, 2009) and starch (Muthukumarasamy et al., 2006; Sultana et al., 2000), but there is an emerging trend towards the use of encapsulation in proteins, such as casein (Heidebach et al., 2009; Oliveira et al., 2007), whey protein (Doherty et al., 2012a; Doherty et al., 2012b; Doherty et al., 2010, 2011) and gelatin (Borza et al., 2010; Li et al., 2009).

An alternative approach to boost the number of probiotic cells in the intestine is by the consumption of a 'prebiotic'. These prebiotics are compounds which are specifically fermented by a probiotic *in vivo*, increasing the number of these cells present in the host (Gibson et al., 2004; Gibson and Roberfroid, 1995). One such prebiotic is BiMuno™, which is comprised of mostly galacto-oligosaccharides (GOS) with degrees of polymerisation (DP) of 2-4, having β 1-3, β 1-4, and β 1-6 linkages, and a disaccharide fraction of α 1-6 galactobiose (Tzortzis et al.,

76 2005). BiMuno™ has been shown to reduce colonisation of pathogenic *Salmonella*
77 *Typhimurium* in mice by Searle *et al* (Searle et al., 2009). The functional components of the
78 BiMuno™ mixture are the GOS which are believed not only to stimulate the growth of
79 probiotic bacteria, but may also be able to interact directly with the subject's immune system.
80 This latter possibility has been touted due to studies in murine BALB/c macrophage models
81 showing up-regulation of cytokines related to immune response, specifically TNF- α and IL-6
82 (Searle et al., 2012). It has been shown by Tzorzis *et al* (Tzorzis et al., 2005) that BiMuno™ had
83 a bifidogenic effect in the colon of pigs, boosting number of *Bifidobacterium spp* by 0.74
84 log(CFU)/mL in the proximal colon, but by only 0.38 log(CFU)/mL in the distal regions of the
85 colon. It was postulated that this imbalance in growth may be caused by the fermentation of
86 GOS by cells in the proximal region, reducing the concentration of the usable GOS further
87 along the gut. A product containing both a pro- and pre- biotic is termed a 'synbiotic', and has
88 been highlighted as a possible means of improving the efficacy of a probiotic supplement. It
89 was the intention of the work herein to produce a microencapsulated synbiotic product
90 containing GOS and a probiotic (*Bifidobacterium breve*), to impart protection to the
91 encapsulated cells and to control the release of the prebiotic across the intestine, which can
92 then act on the hosts indigenous microflora.

93 The production of an encapsulated synbiotic has several different challenges compared to the
94 formulation of the probiotic alone. One particular advantage of encapsulating GOS, compared
95 to probiotic cells, is that relatively harsh processing conditions during the encapsulation step
96 may be used. However, for a synbiotic containing GOS and probiotic cells, careful
97 consideration must be taken in order to ensure the applicability of the system to both
98 bioactives. In order to improve the survival of cells through the stomach, probiotics have been
99 microencapsulated into alginate polysaccharide gels, which have been modified by various
100 methods (Chandramouli et al., 2004; Chavarri et al., 2010; Cook et al., 2012; Cui et al., 2007;

101 Graff et al., 2008). It has been shown that coating alginate microcapsules with one or more
102 layers of chitosan leads to an improvement in the survival of probiotic cells during exposure to
103 acid (Chavarri et al., 2010; Cook et al., 2011; Doherty et al., 2012a; Liserre et al., 2007). It has
104 also been demonstrated that the incorporation of other materials, such as starch, into the
105 alginate matrix can affect the microcapsule properties (Homayouni et al., 2008; Sultana et al.,
106 2000). In this paper, a multiparticulate microencapsulation system was devised to offer
107 controlled release to GOS, and protection of *B. breve* to acid. This consisted of individually
108 microencapsulated BiMuno™, which was then incorporated into a chitosan-coated alginate gel
109 containing *B. breve*, a model probiotic strain. The GOS was encapsulated into a separate
110 system which offers a time-dependent release of small molecules, as the alginate
111 microencapsulation system is too porous to contain the GOS contained in BiMuno™.

112 Poly(D,L-Lactic-co-Glycolic acid) (PLGA) was identified as a plausible material for the time-
113 dependent release of GOS. PLGA was chosen as an encapsulating material as it is highly
114 biocompatible, FDA-approved, and has been shown to control the release of water-soluble
115 drugs, extending their delivery from hours (Wischke and Schwendeman, 2008) up to months
116 (Corrigan and Li, 2009). The biodegradation process occurs simply in solution by hydrolysis of
117 the ester linkages between the monomers. This results in the breakdown of the polymer
118 chains into lactic and glycolic acid, both of which are easily metabolised in the body.

119 There have been a number of multiparticulate dosage forms reported in the literature for the
120 targeting of drugs to the intestine. Eudragit-coated PLGA particles containing budesonide have
121 been fabricated by Krishnamachari *et al* (Krishnamachari et al., 2007). These particles were
122 intended to deliver the encapsulated drug to the colon, and showed impressive steady release
123 of drug over 25 hours. There has also been a study of alginate-PLGA multiparticulates for the
124 delivery of silymarin (El-Sherbiny et al., 2011). These delivery devices consisted of PLGA
125 nanoparticles, produced through a single emulsion solvent evaporation technique, which were

126 incorporated into alginate matrices through the conventional ionotropic gelation method. *In*
127 *vitro* GI release studies found that approximately 80 % of encapsulated silymarin was delivered
128 over around 10 hours. The release was pH dependent, with a clear targeting of delivery to
129 simulated intestinal solution. After the change of pH there was a release of up to 50 % of
130 silymarin over the course of 2 hours.

131 It should be noted that diarrhoea is common in bowel disorders, which may lead to
132 premature clearing of microparticles. It has been found that clearing due to diarrhoea is size-
133 dependent and that particles of less than 200 microns are retained more effectively during
134 diarrhoea, thus, it is important that microparticles are produced with diameters lower than
135 this threshold (Lamprecht et al., 2004).

136 This work aimed to develop a multiparticulate system to encapsulate a synbiotic combination
137 of GOS and *B.breve*. The development of PLGA-GOS microcapsules will be discussed, followed
138 by characterisation of particle size and morphology using microscopy. The release of GOS from
139 these particles in simulated GI conditions was then evaluated and the system expanded to a
140 multiparticulate containing probiotic cells, with associated cell and GOS release data.

141 **2.0 Materials and methods**

142 **2.1 Materials**

143
144 Sodium alginate (19-40 kDa, M:G ratio 3.3 ± 0.3 (Wright et al., 2012)), low molecular-weight
145 chitosan (103 kDa, degree of deacetylation: 85.6 %) and fluorescein isothiocyanate (FITC) were
146 purchased from Sigma-Aldrich (Gillingham, U.K.). *Bifidobacterium breve* NCIMB 8807 was
147 purchased from the National Collection of Industrial Food and Marine Bacteria (Aberdeen,
148 U.K.). Wilkins-Chalgren (WC) anaerobe agar and phosphate-buffered saline (PBS) were
149 purchased from Oxoid (UK). PLGA 5002A was purchased from PURAC (Gorinchem,
150 Netherlands). This grade of PLGA was chosen as it had a relatively quick time for complete

151 biodegradation, 0.5-1 month(s). The manufacturer's guide gave an Mw of 17 kDa.
152 Dichloromethane (DCM) was purchased from Sigma-Aldrich (U.K.). BiMuno™ was provided by
153 Clasado Research Services Ltd (Reading, U.K.) as a 68 % (w/v) aqueous syrup. Simulated
154 gastrointestinal (GI) solutions were made according to the United States Pharmacopeia,
155 without enzymes. Adjustments to pH are shown in brackets after solution name. Chitosan
156 solutions were at 0.4 % w/v in 0.1 M acetic acid and the pH adjusted to pH 6.0 with 1 M NaOH.

157 **2.2 Production of PLGA microcapsules containing GOS**

158 The microencapsulation of GOS was attempted by a solvent evaporation technique (Herrmann
159 and Bodmeier, 1995). To form the WOW emulsion, 0.5 mL aqueous BiMuno™ solution of a
160 known concentration was added to 10 mL PLGA solution (10 % w/v) in DCM with overhead
161 stirring at 1200 rpm for 60 s. This primary emulsion was then transferred into 100 mL aqueous
162 alginate solution (1 % w/v) with overhead stirring at 1200 rpm, resulting in the formation of a
163 secondary WOW emulsion. The WOW emulsion was then left to stir at room temperature for
164 60 min which allowed the evaporation of DCM. After 60 min of stirring, microcapsules were
165 collected via centrifugation at 1,000 rpm for 10 min, twice washed with 50 mL deionised water
166 and freeze-dried (Thermo LL3000) to allow removal of water from the discrete phase. Samples
167 were then stored in a desiccator before use. Scanning electron microscopy (SEM) was
168 performed on the samples to examine their structure. The initial experiment conducted was
169 simply to establish the relationship between particle size and the concentration of BiMuno™
170 used. BiMuno™ solutions of 10, 20 and 30 % (w/v) were prepared and used as the internal
171 water phase in the procedure above. The particles produced were then sized by observation
172 on a light microscope (Leica DM2500). The diameter of 100 particles was measured using
173 ImageJ.

174

175 **2.3.0 Release of GOS from PLGA microcapsule in *in vitro* GI solutions**

176 **2.3.1 Ion-exchange HPLC of BiMuno™**

177 BiMuno's GOS components were analysed by ion-exchange HPLC. In order to quantify GOS in
178 the following release experiments, a Rezex RCM-monosaccharide column (Phenomenex, U.K.)
179 was used, running HPLC-grade water at a flow rate of 0.5 mL/min with an oven temperature of
180 85 °C (Fig 1s, Supporting information). However, this HPLC technique was very sensitive to
181 salts, especially phosphates, present in the GI solutions. The salts were removed from solution
182 using an amino-column running 60 % v/v acetonitrile in water at a flow rate of 1 mL/min with
183 an oven temperature of 30 °C. The GOS peak could then be separated from phosphate salts
184 using a fraction collector and the solvent removed from solution by heating in an oil bath (50
185 °C, until complete evaporation). The resulting residue was dissolved in a volume of pure water
186 equal to that injected (200 µL) and was analysed once more by the ion-exchange method. This
187 method led to a significant (52.9 ± 2.6 %), but reproducible loss of GOS, which could be
188 corrected for during determination of GOS concentration in simulated GI solutions. It should
189 also be clarified that when describing the data from these release experiments the GOS
190 concentration is given as a percentage of the theoretical maximum GOS content assuming 100
191 % encapsulation efficiency.

193 **2.3.2 Quantification of GOS release in simulated GI solutions**

194 GOS-containing PLGA microcapsules were produced as above and re-suspended in 10 mL
195 simulated gastric solution (at pH 2.0). This solution was then incubated at 37 °C with shaking at
196 100 rpm for 60 min. A sample was then taken through a syringe and microfilter to ensure that
197 no microcapsules were drawn into the syringe. The particles in solution were then centrifuged
198 at 1,000 rpm for 10 min, the simulated gastric solution removed and the particles re-
199 suspended in 50 mL simulated intestinal solution (pH 6.0) to simulate entry to the small
200 intestine, and incubated as before. After 60 min of incubation a sample was taken and the
201 particles in solution centrifuged, the supernatant removed and the resulting pellet re-

202 suspended in 50 mL simulated intestinal solution (pH 7.2) to simulate the pH of the distal small
203 intestine, and incubated. After 120 min at this pH a sample was taken. This two stage process
204 was attempting to approximate the pH, temperature and duration of small intestinal passage,
205 following gastric passage. The microcapsules were then removed from solution by
206 centrifugation and re-suspended in 50 mL simulated intestinal solution (pH 5.5), which
207 intended to simulate the pH of the proximal colon. Samples (2 mL) were then taken at
208 numerous time points for up to 12 days. After each sample was taken, an equivalent volume
209 of simulated GI solution (2 mL) was added to replace that loss. An overview of this simulated
210 GI passage is shown in the supplementary information (Fig. 2s).

211

212 **2.4 Effect of discrete aqueous phase volume on release rate of GOS from PLGA microcapsules**

213

214 PLGA microcapsules containing GOS were prepared as before, but with 0.5, 1.0 and 2.0 mL
215 BiMuno™ solution (20 % w/v) added during the formation of the primary emulsion. These
216 microcapsules were then put through the simulated GI passage described previously. The
217 encapsulation efficiency of the 1.0 mL internal phase microcapsules was estimated by the
218 measurement of GOS in the continuous alginate phase.

219

220 **2.5.0 Release of GOS from alginate and alginate-chitosan microcapsules**

221 In order to evaluate the effect of alginate microencapsulation on the release of GOS, an *in*
222 *vitro* GI passage was used. A solution containing 2 % w/v BiMuno™ and 2 % w/v alginate was
223 prepared. 1 mL of this solution was extruded with a syringe and pump (2 mL/min) into 50 mL
224 CaCl₂ solution (0.05 M) and left to harden for 30 min. Then, in the case of chitosan-coated
225 capsules, the hardened sample was placed into chitosan solution for 10 min to allow coating of
226 the samples. The capsules were then dried by fluid-bed drying for 15 min at 30°C, with an

227 airflow at 50 % power. To evaluate the release of GOS from these particles, the *in vitro* GI
228 passage previously described was used. However, the study was halted before the final section
229 (pH 5.5) due to the complete dissolution of the microcapsules.

230

231 ***2.5.1 Purification of GOS samples revisited***

232 Due to the incompatibility of alginate with the eluent in the purification procedure used
233 previously, a new purification procedure was used for the experiments involving alginate.
234 Samples (10 mL) were adjusted to pH 7-7.5, with a measured volume of NaOH (1 M). To these
235 samples 10 mL CaCl₂ (0.05 M) was added, at which point the solutions became cloudy due to
236 the formation of insoluble calcium phosphate and calcium-alginate. The solution could then be
237 microfiltered (0.45 µm filter), removing the phosphates and alginate present. These samples
238 could then be analysed by ion-exchange HPLC. This method was validated before use by the
239 purification of a known concentration of BiMuno™, giving full recovery of GOS.

240

241 **2.6 Release of GOS from alginate and alginate-chitosan encapsulated PLGA multiparticulates**

242 The previously evaluated GOS/PLGA microcapsules were prepared as before and placed into
243 10 mL alginate solution (2 % w/v) with stirring before extrusion into 500 mL CaCl₂ solution
244 (0.05 M) with a syringe and pump (2 mL/min). These multiparticulate capsules were allowed to
245 harden for 30 min and, in the case of chitosan-coated capsules, placed in 0.4 % w/v chitosan
246 solution for 10 min. The capsules were then dried by fluid-bed drying as before. Fluid-bed
247 dried microcapsules were stored in a desiccator until use. These multiparticulates were then
248 run through the same *in vitro* GI transit model used for the GOS/PLGA microcapsules,
249 shortened to 72 h, due to the likelihood of excretion *in vivo* by this point. Additionally, due to
250 the larger sample size, volumes of simulated GI solutions used were multiplied ten-fold.

251 Samples (10 mL) were collected as previously described and taken for purification before
252 analysis.

253

254 **2.7 Viability and release of *B. breve* encapsulated in synbiotic microcapsules**

255 To determine whether the final prebiotic system would also allow the survival of cells, an *in*
256 *vitro* test was conducted. *B. breve* was grown at 37 °C for 72 h, anaerobically on WC anaerobe
257 agar before inoculation into 10 mL TPY broth. The inoculated cell suspension was grown at 37
258 °C for 22 h, before centrifugation at 3200 rpm for 15 min at 4 °C. The supernatant was
259 removed and the cell pellet re-suspended in sufficient 2 % w/v microfiltered alginate solution
260 to OD₆₀₀ ~2.0. To 10 mL of this polymer/cell solution, PLGA microcapsules containing GOS were
261 added, produced with 1 mL internal phase as previously described, with stirring. This solution
262 was extruded using a syringe and pump (flow rate 2.0 mL/min) into 50 mL CaCl₂ (0.05 M) and
263 left in solution to harden for 30 min. Microcapsules were then coated with 1 layer of chitosan
264 as described in a previous publication (Doherty et al., 2012a). These synbiotic multiparticulates
265 were then dried by fluid-bed drying for 15 min at 30 °C, and airflow at 50 % of full power. The
266 microcapsules were then put through the simulated GI transit described previously. Samples
267 taken were assessed for live cell content by plate counts on WC agar. This gave a
268 representation of the numbers of cells surviving in the low pH gastric solution and the rate of
269 release of these cells.

270

271 **2.8 Scanning electron microscopy**

272 SEM was performed on samples throughout various stages of this article. Typically, samples
273 were prepared for SEM by drying, followed by adhesion to a carbon stub and sputter coating
274 with gold. SEM was performed on an FEI Quanta 600 FEG environmental SEM under high-

275 vacuum and using a point size of 3. The images presented in Fig.1 used a 5.0 kV electron beam,
276 all other images were taken using a 20 kV electron beam.

277

278 **2.9 Statistical analysis**

279 Where used, statistical significance was determined by one-way ANOVA with Tukey's post-hoc
280 test using Graphpad Prism (USA).

281

282 **3.0 Results and discussion**

283 **3.1 Production and sizing of PLGA microcapsules**

284 The production of PLGA microcapsules containing GOS was achieved using a solvent
285 evaporation technique based on the modification of known methods (Herrmann and
286 Bodmeier, 1995). Observation of these microcapsules using SEM revealed that the
287 microcapsules were spherical with a smooth surface (Figure 1). The sample appears relatively
288 polydisperse, and any damaged capsules showed that the microcapsules were hollow with a
289 dense crust with a thickness of approximately 1 μm (measured by ImageJ).

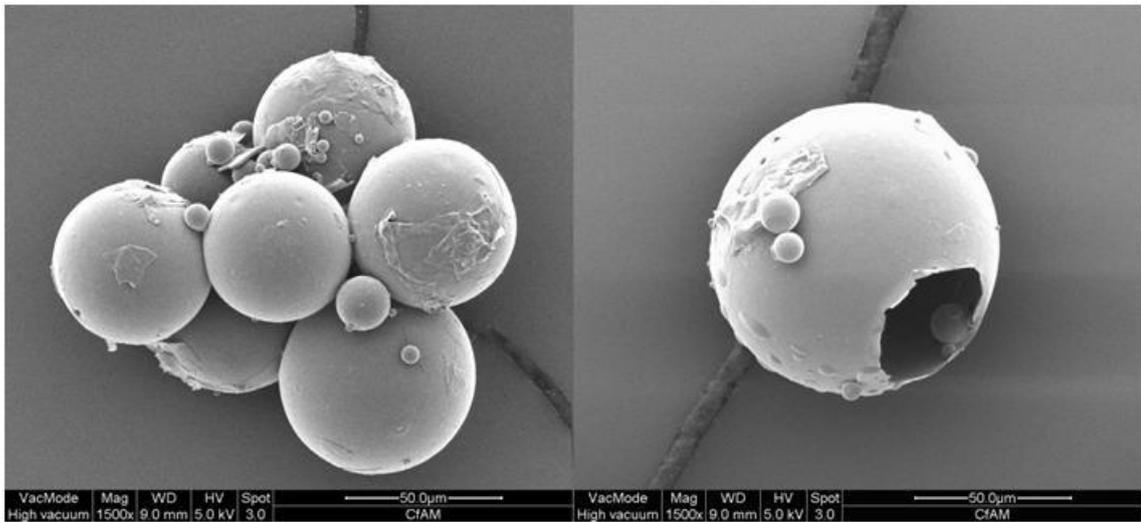


Figure 1: SEM images of PLGA microcapsules containing GOS. Please note that the damage seen on the right image is atypical for this sample, and was chosen to demonstrate that the capsules were hollow.

The effect of BiMuno™ concentration on the average particle size and distribution was determined by light microscopy and subsequent image analysis using ImageJ. This data, shown in Table 1, is represented as the mean diameter and polydispersity index (PDI) of three separate batches of microcapsules. The PDI is defined as:

$$PDI = (\text{standard deviation}/\text{mean})^2$$

It is clear from this experiment that increasing the concentration of BiMuno™ from 10 to 20 % (w/v) resulted in a greater than two-fold decrease in the particle diameter. Increasing the concentration to 30 % (w/v) did not have a significant effect on the particle diameter. There was no significant difference in the polydispersity of the particles between conditions. The polydispersity of the sample could have consequences on the release rate of GOS from these particles. The release rate should be dependent in part on the size of the microcapsules (Klose et al., 2006), so it is important to attempt to make the particle size as regular as possible. As

307 there was no difference between the 20 and 30 % GOS samples, 20 % GOS was taken on for
 308 further experimentation. It should be noted that the concentration of GOS in the internal
 309 phase may affect the encapsulation efficiency of the system (Mao *et al*, 2007), and may be a
 310 factor which could be optimised in terms of encapsulation efficiency, as well as particle size.

311 **Table 1:** Effect of GOS concentration on PLGA particle size and PDI. Data given as mean \pm
 312 standard deviation (n=3). Superscript letters separate values which are significantly different
 313 (p<0.05).

BiMuno™ in internal phase (%)	Particle diameter (μm)	PDI
10	97.3 \pm 9.1 ^a	0.6 \pm 0.1 ^c
20	45.2 \pm 5.3 ^b	0.4 \pm 0.1 ^c
30	44.8 \pm 3.7 ^b	0.5 \pm 0.1 ^c

314


315 **3.2 Release of GOS from PLGA microcapsules during exposure to simulated GI solutions**

316

317 The release of GOS from these GOS/PLGA microcapsules under *in vitro* GI conditions was
 318 measured by ion-exchange HPLC. These studies were initially conducted over a lengthy time
 319 period, to understand the full release profile of PLGA microcapsules containing GOS. 12 days
 320 incubation in simulated intestinal solution gave a triphasic release profile (Figure 2). The initial
 321 phase of release (0-6 h) was likely caused by the diffusion of GOS through pores or the
 322 polymer itself. This was followed by a second phase of very little release (6-24 h) at which
 323 point the GOS able to diffuse had diminished and the PLGA chains were slowly hydrolysing.
 324 The third phase of release (24-288 h) was the result of the erosion of the particles as the
 325 molecular weight of PLGA reduced to such a degree that it became water-soluble. This
 326 triphasic release profile predicts that around 25 % of GOS (19 mg GOS/g particles) should be
 327 released after 6 h intestinal transit. This transit time should cover gastric and small intestinal
 328 transit (approximately 4.5 h) and the beginnings of large intestinal passage. The second phase

329 of release should occur during the remainder of large intestinal transit, however, very little
330 GOS release occurs during this time. The third phase of release would not be reached in the
331 body unless the PLGA particles were very effectively retained after accumulation in ulcers, as
332 has been reported for PLGA microcapsules (Schmidt et al., 2013). This triphasic release profile
333 has been reported by other groups working on hollow PLGA particles (Cohen et al., 1991;
334 Sturesson et al., 1993).

335

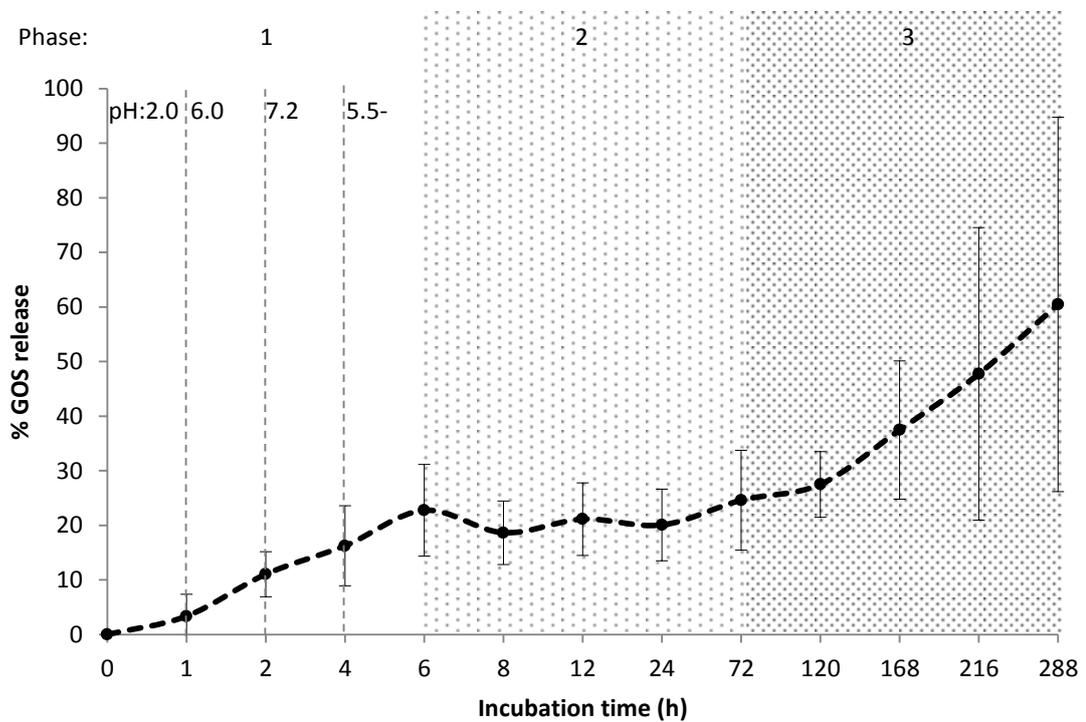


336

337 **Figure 2:** Release of GOS from PLGA microcapsules, expressed as a percentage of GOS initially
338 added to emulsion. Results given as mean \pm standard deviation (n=4). Please note that the x-
339 axis is not linear.

340

341 3.3 Effect of internal phase volume on the porosity and release of GOS from PLGA 342 microcapsules

343 After the initial study, attempts were made to increase the rate of release of GOS from these
344 materials in order to try and recover greater amounts of GOS from these devices during GI
345 passage. Work conducted by Schlicher *et al* (Schlicher et al., 1997) and Mahboubian *et al*
346 (Mahboubian et al., 2010) found that increasing the volume of the internal phase in WOW
347 prepared PLGA microcapsules with increased their apparent surface porosity. It is believed
348 that this increase in surface porosity results in an increased rate of drug release from the
349 microcapsules. The internal phase volume was increased from 0.5 mL to 1.0 and 2.0 mL, and
350 the microcapsules' apparent porosity was examined using SEM (Figure 3), revealing a great
351 increase in porosity as the internal phase volume was increased to 2.0 mL. This was consistent
352 with the literature available and was attributed to the increased probability of finding droplets
353 of internal phase close to the boundary of the capsules during the microcapsule formation
354 process (Herrmann and Bodmeier, 1995). This work by Herrmann and Bodmeier (Herrmann
355 and Bodmeier, 1995) also raises the possibility of the thinning of the PLGA crust in higher
356 internal phase volume microcapsules due to the initial enlargement of emulsion droplets.

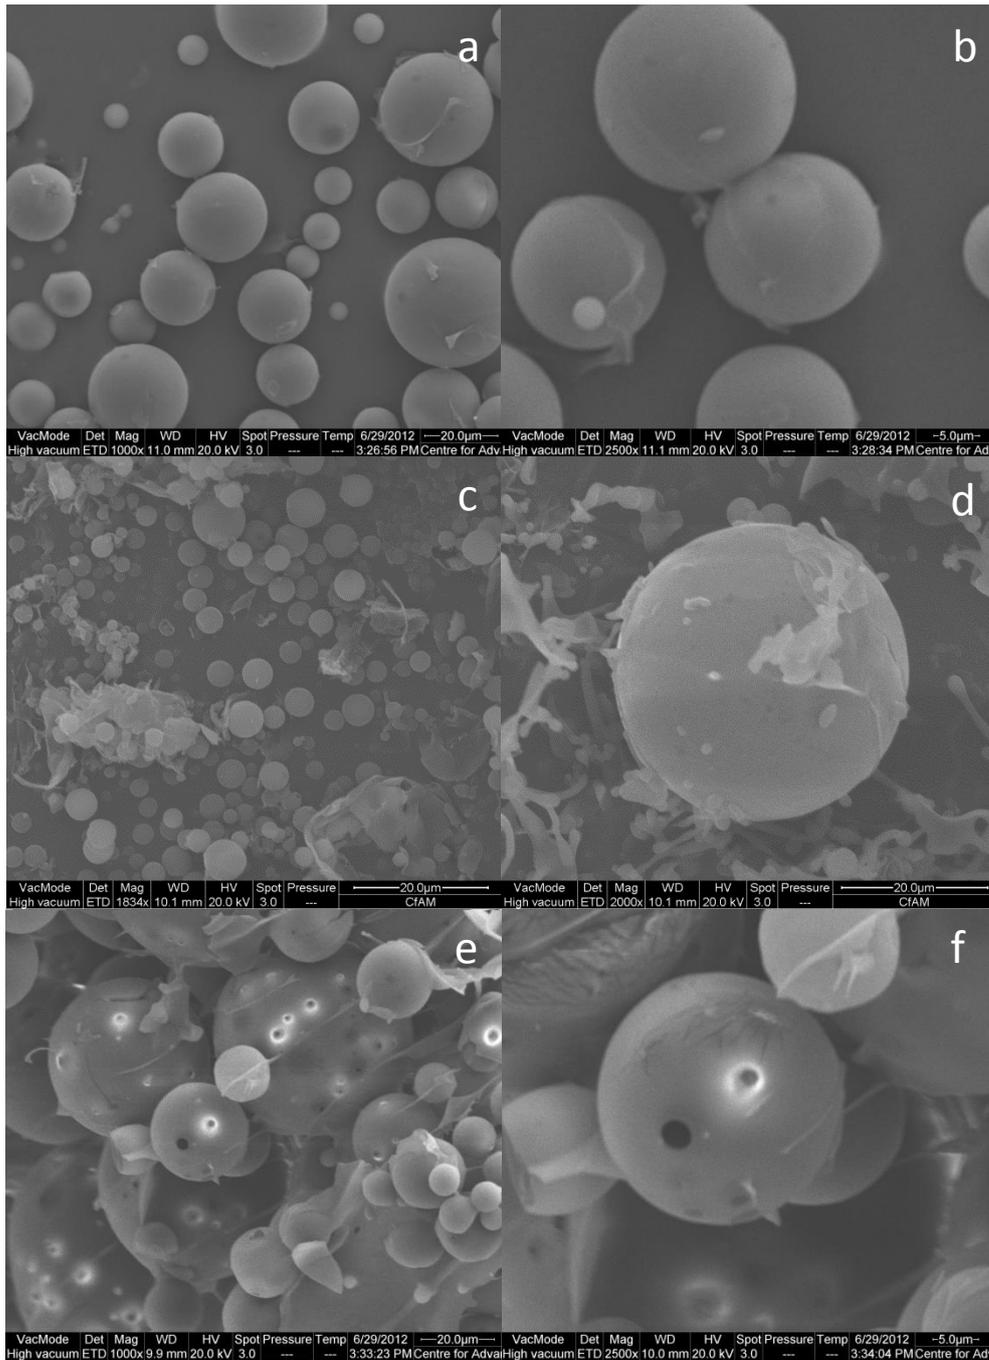

357

358

359

360

361

362

Figure 3: SEM images showing the morphology of microcapsules prepared with 0.5 mL (a,b), 1.0 mL (c,d) and 2.0 mL (e,f) internal phase volume (top to bottom).

In vitro GI transit was conducted with the microcapsules prepared with 1.0 and 2.0 mL internal phase volume in order to establish whether this increase in internal phase would be met with

363 a change in the release profile. These experiments (Figure 4) reveal that increasing the internal
364 phase from 0.5 to 1.0 mL led to a slight increase in the percentage of GOS released over the
365 first 6 hours of testing, from 24.40 ± 5.21 % to 36.11 ± 2.33 % (the latter correlating to $55.00 \pm$
366 3.52 mg GOS/g particles). This time period corresponds to the first phase of release outlined
367 above and theoretically corresponds to stomach and small intestine transit time, and a portion
368 of the distal colon. Increasing the internal phase volume further resulted in a very large
369 reduction in the amount of GOS released during this phase, with only 10.30 ± 1.13 % GOS
370 released. As this release does not take into account the encapsulation efficiency of the system,
371 this data is also a reflection of the encapsulation efficiency of the system. The high porosity of
372 the microcapsules seen in Fig 3e and f has presumably lead to a low encapsulation efficiency
373 of the GOS in this case, which is reflected in the low concentration seen in the release data.
374 The microcapsules containing 1.0 mL internal phase were taken forward for further analysis
375 due to the slightly improved release profile and higher loading obtained. Direct measurement
376 of the encapsulation efficiencies of the microencapsulation system was challenging, so, the
377 data has been presented as the percentage of GOS released, relative to that put into the
378 system. The encapsulation efficiency of the 1.0 mL system was estimated to be 90 % by
379 measuring the GOS present in the continuous alginate phase, i.e. the GOS not encapsulated
380 into the microparticles. The encapsulation efficiency was calculated using the formula:
381 $\text{encapsulation efficiency} = 100 - 100(\text{GOS present in continuous phase} / \text{quantity of GOS added})$.


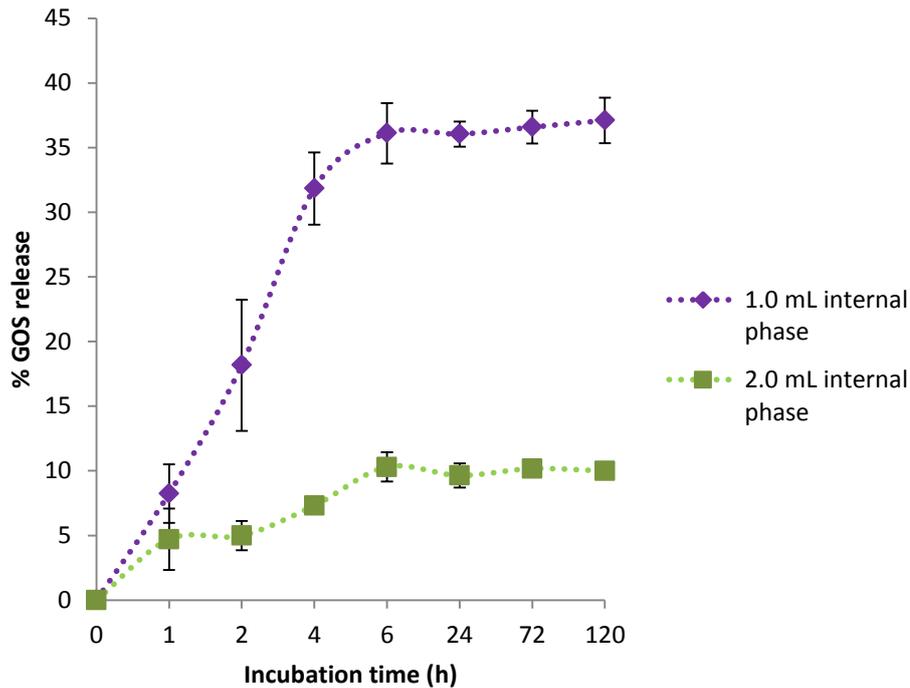


Figure 4: Effect of internal phase volume on the release of GOS from GOS/PLGA

microcapsules. Data given as mean and standard deviation (n = 3). The position in the GI tract simulated is overlaid. Please note that the x-axis is not linear.

3.4 Production and evaluation of PLGA/alginate multiparticulates

The next step in the production of the intended synbiotic microcapsules was the incorporation of the 1.0 mL internal phase PLGA microcapsules into alginate gels. This can be simply achieved by the co-extrusion of alginate and the PLGA microcapsules into CaCl₂. Alginate-PLGA microcapsules were produced by this method, dried by fluid-bed drying and their structure observed using SEM (Figure 5). The SEM observation of fluid-bed dried alginate/PLGA multiparticulates revealed that the outer surface appeared to be highly occupied by PLGA particles. The internal structure was dense and showed clear evidence of PLGA microcapsules present within the matrix. It was also observed that the product was of a greater sphericity than the alginate microcapsules produced in a previous publication (Cook et al., 2011). This was most likely due to the PLGA microcapsules acting as a ‘filler’ in a similar manner to starch, reported widely in the literature (Chan et al.).

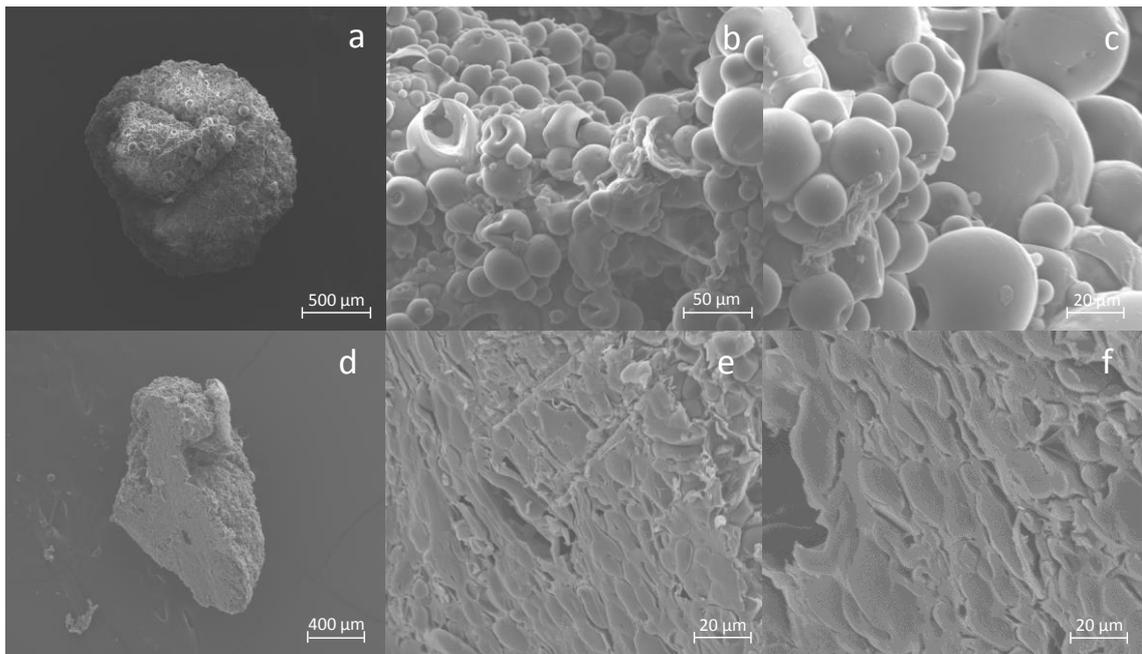

398


399 **Figure 5:** Fluid-bed dried alginate/PLGA multiparticulates observed using SEM. The external
400 surface is shown at 50x (a), 500x (b) and 1000x (c) magnification. The internal structure is then
401 shown at 50x (d), 500x (e) and 1000x (f) magnification

402 In order to establish the release profile of GOS from the alginate/PLGA multiparticulates, the
403 same *in vitro* method was used as for the PLGA particles alone. However, the purification
404 process used previously was not applicable to solutions containing alginate as the
405 polysaccharide is incompatible with the required eluent. A new method of purification was
406 established, and it was found that the addition of a stoichiometric amount of calcium chloride
407 led to the cross-linking of alginate and formation of an insoluble calcium phosphate. Both of
408 these contaminants could be removed from solution by microfiltration. The formation of
409 insoluble calcium phosphate was pH dependent; all samples were adjusted to pH 7.0 with a
410 known volume of 1 M NaOH, so that the final data could be adjusted to take this volume
411 change, and the volume of calcium chloride added, into account. This method led to a
412 recovery of 95.3 ± 1.7 % of GOS when a solution of 2 mg/mL BiMuno™ in simulated intestinal
413 solution (pH 7.0) with 1 % alginate added was purified.

414 To establish the effect of the polysaccharides alone, alginate and alginate-chitosan
415 microcapsules were loaded with GOS and fluid-bed dried before being put through the
416 simulated GI passage. The rate of GOS release with time was established using the previously
417 described method of purification (Fig. 3s, Supplementary Information). The data shown allows
418 two conclusions to be drawn; the encapsulation efficiency (i.e. the percentage of GOS added
419 to the emulsion that was present in the final product) of GOS is very low and there was only a
420 small control of release. This means that alginate and alginate-chitosan could not be used
421 individually to deliver GOS in large amounts. The low encapsulation efficiency is
422 understandable due to the length of time these materials are left to harden in calcium
423 chloride, during which there will be diffusion of GOS from the matrix. As the cross-linking
424 density of the alginate matrix increases with time, the diffusion of GOS out of the alginate
425 would be most pronounced during the early stages of gelation, when the 'porosity' of the
426 material is very high due to the low cross-linking density. Comparison of alginate and alginate-
427 chitosan does not yield any apparent differences in the rate of release of GOS, but it does
428 appear that GOS loading into alginate microcapsules is higher, which would be a result of
429 further diffusion of GOS out of the particles during the chitosan coating process. It should be
430 noted, however, that the errors associated with the data make comparison of alginate to
431 alginate-chitosan difficult. The encapsulation efficiencies were calculated, using the final
432 reading of this experiment as the materials had completely dissolved, as 0.7 ± 0.2 % and $0.5 \pm$
433 0.2 % for alginate and alginate-chitosan, respectively.

434 GOS/PLGA multiparticulates were put through the *in vitro* GI model previously described and
435 GOS release evaluated using the new purification method. The results in Figure 6 show that
436 the level of release of GOS was not greatly affected by further encapsulation into alginate or
437 alginate-chitosan, but there did appear to be a slight delay of release. In the case of the
438 alginate-chitosan system the apparent change in release profile was greater, with some


439 release appearing to occur between 12-24 h, but the change was within error so conclusions
 440 are difficult to be drawn. Another, slightly unusual advantage of encapsulating the PLGA
 441 microcapsules was also observed. Prior to alginate encapsulation the PLGA microcapsules
 442 floated in solution, as seen in the *in vitro* studies for the PLGA capsules alone. The
 443 microcapsules would float for several hours before sinking, presumably due to sufficient water
 444 uptake. After encapsulation, the formulation would sink, and by dissolution of the alginate the
 445 PLGA microcapsules had apparently taken up sufficient water to not float. Whilst this seems
 446 initially trivial, *in vivo* this would result in the retention of the formulation in the stomach, as is
 447 the intention of floating delivery devices (Kawashima et al., 1992), so that the PLGA
 448 microcapsules would release a larger fraction of their load into the stomach.

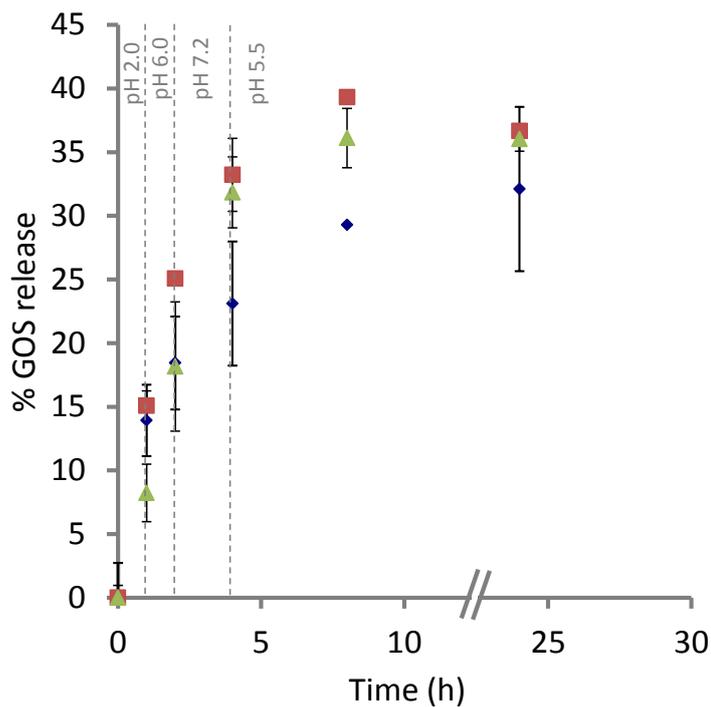

449
 450 **Figure 6:** Release of GOS from PLGA/alginate (blue diamonds) and PLGA/alginate-chitosan
 451 (red-squares) multiparticulates during simulated GI passage. The release of GOS from PLGA
 452 microcapsules containing 1 mL internal phase overlaid (green triangles). Data given as mean \pm
 453 standard deviation (n=3).

3.5 Incorporation of *B.breve* into PLGA/alginate multiparticulates

Finally, to ensure that the inclusion of PLGA microcapsules did not adversely affect the ability of the alginate microcapsules to protect the cells, *B. breve* was included into the multiparticulate alginate matrices in which the GOS/PLGA microcapsules were also incorporated. These microcapsules were coated with chitosan in order to evaluate the effect of coating on these materials. Coating with chitosan has previously shown efficacy in improving protection from gastric acid (Doherty et al., 2012a). This system was then run through the simulated GI passage described previously, with cell counts taken from solution. This should give an idea of both the number of cells surviving in gastric solution, and the rate of release of cells from these materials. Results displayed in Figure 7, show higher cell numbers surviving in the chitosan coated multiparticulate system relative to that predicted by cell survival after encapsulation in chitosan-coated alginate microcapsules without GOS/PLGA. It has been found that after encapsulation in alginate-chitosan and fluid-bed drying, 6.6 ± 0.5 log CFU/mL cells of *B.breve* survived 1 h in simulated gastric solution (Cook et al., 2011). The data in Figure 7 suggests that up to 8.0 ± 0.3 log CFU/mL cells survived when GOS/PLGA was included into the formulation, which was statistically different by T-testing ($p < 0.001$). Without encapsulation, it is known that *B.breve* survives for less than 1 h in gastric solution (Cook et al., 2011). One possible explanation for the increase in the number viable cells found after exposure to gastric conditions could be the large number of hydrophobic PLGA microcapsules found on the surface of the alginate matrix. This could act as a hydrophobic coat, reducing the water-permeability of the capsules. The particles on the surface could also simply reduce the surface area of the permeable alginate capsules, thereby slowing the rate of acid diffusion into the matrix. It is also possible that there is some influence from the encapsulated GOS, stimulating the growth of cells, but this was thought less likely due to the absence of other nutrients needed to start cell division.

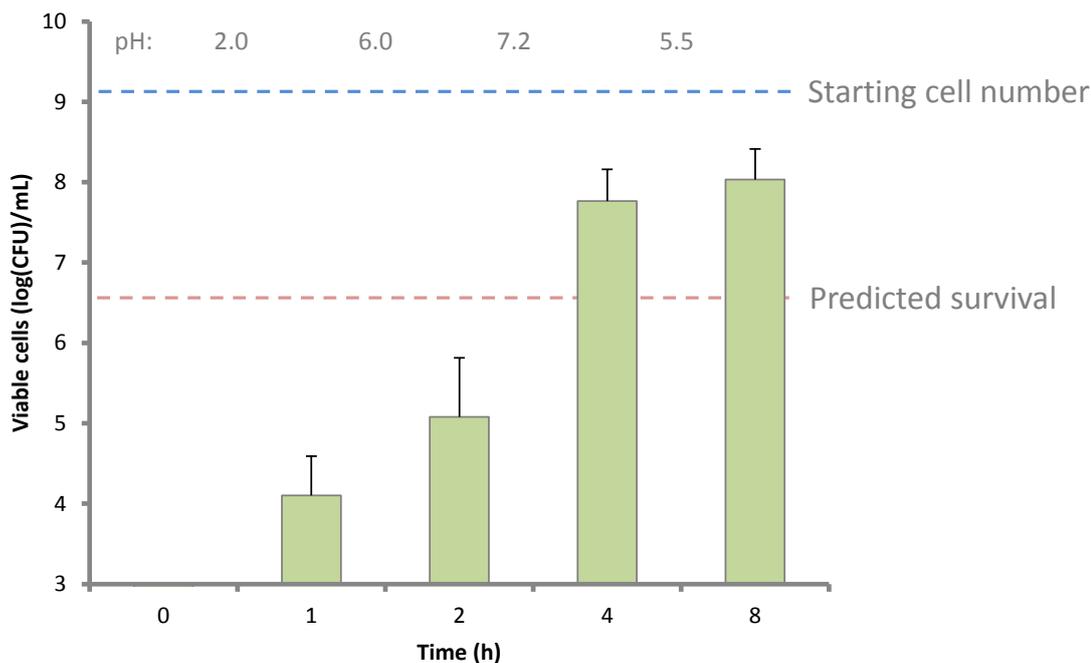

479

480 **Figure 7:** Release of viable *B. breve* from PLGA/alginate multiparticulates with a single layer of
 481 chitosan in simulated GI conditions, relative to the survival predicted by chitosan-coated
 482 alginate microcapsules. Survival is predicted based on alginate-chitosan systems without
 483 PLGA/GOS microcapsules incorporated. Limit of detection: 3 log(CFU)/mL. Data given as mean
 484 and standard deviation (n=3). Please note that the x-axis is not linear.

485

486 **4.0 Concluding remarks**

487 GOS was successfully encapsulated into hollow PLGA microcapsules. These microcapsules
 488 were able to control the release of GOS, giving a triphasic release profile during *in vitro* GI
 489 conditions in which around 25 % of the GOS initially added was released over 6 h. *In vivo* this
 490 timescale should correlate approximately to gastric transit, small intestinal transit and early
 491 large intestinal transit. The porosity of these microcapsules could be varied by altering the
 492 internal phase volume of the microcapsules, but did not affect the rate of release to the

493 degree needed to move to a single-phasic release profile. From the volumes used, the largest
494 quantity of GOS delivered in the first phase of release was 36 %, achieved with 1 mL internal
495 phase volume. It is possible that in future the release and drug loading of these particles could
496 be optimised by further examination of the processing parameters and PLGA/GOS
497 concentrations. The incorporation of GOS/PLGA microcapsules into alginate and chitosan-
498 coated alginate microcapsules gave similar results to the GOS/PLGA microcapsules alone, with
499 a small extension of release seen in the chitosan coated capsules. Incorporation into alginate
500 systems halted the floatation of the formulation, which would alter the distribution of the GOS
501 *in vivo*. Expanding this system to also include *B. breve* resulted in a higher survival of cells
502 when exposed to simulated gastric solution, which is believed to be, in part, due to the
503 increased hydrophobicity of the materials after the incorporation of PLGA microcapsules.

504

5.0 Acknowledgements

Clasado Ltd are thanked for funding this project and providing BiMuno™.

6.0 References

Borza, A.D., Annan, N.T., Moreau, D.L., Allan-Wojtas, P.M., Ghanem, A., Rousseau, D., Paulson, A.T., Hansen, L.T., 2010. Microencapsulation in genipin cross-linked gelatine-maltodextrin improves survival of *Bifidobacterium adolescentis* during exposure to in vitro gastrointestinal conditions. *J. Microencapsulation* 27, 387-399.

Chan, E.-S., Wong, S.-L., Lee, P.-P., Lee, J.-S., Ti, T.B., Zhang, Z., Poncelet, D., Ravindra, P., Phan, S.-H., Yim, Z.-H., Effects of starch filler on the physical properties of lyophilized calcium-alginate beads and the viability of encapsulated cells. *Carbohydr. Polym.* 83, 225-232.

Chandramouli, V., Kailasapathy, K., Peiris, P., Jones, M., 2004. An improved method of microencapsulation and its evaluation to protect *Lactobacillus* spp. in simulated gastric conditions. *J. Microbiol. Meth.* 56, 27-35.

Chavarri, M., Maranon, I., Ares, R., Ibanez, F.C., Marzo, F., Villaran Mdel, C., 2010. Microencapsulation of a probiotic and prebiotic in alginate-chitosan capsules improves survival in simulated gastro-intestinal conditions. *Int. J. Food Microbiol.* 142, 185-189.

Cohen, S., Yoshioka, T., Lucarelli, M., Hwang, L.H., Langer, R., 1991. Controlled delivery systems for proteins based on poly(lactic/glycolic acid) microspheres. *Pharm. Res.* 8, 713-720.

Cook, M.T., Tzortzis, G., Charalampopoulos, D., Khutoryanskiy, V.V., 2011. Production and evaluation of dry alginate-chitosan microcapsules as an enteric delivery vehicle for probiotic bacteria. *Biomacromolecules* 12, 2834-2840.

Cook, M.T., Tzortzis, G., Charalampopoulos, D., Khutoryanskiy, V.V., 2012. Microencapsulation of probiotics for gastrointestinal delivery. *J. Control. Release* 162, 56-67.

Cook, M.T., Tzortzis, G., Khutoryanskiy, V.V., Charalampopoulos, D., 2013. Layer-by-layer coating of alginate matrices with chitosan-alginate for the improved survival and targeted delivery of probiotic bacteria after oral administration. *J. Mater. Chem. B* 1, 52-60.

Corrigan, O.I., Li, X., 2009. Quantifying drug release from PLGA nanoparticulates. *Eur. J. Pharm. Sci.* 37, 477-485.

Cui, J.H., Cao, Q.R., Lee, B.J., 2007. Enhanced delivery of bifidobacteria and fecal changes after multiple oral administrations of bifidobacteria-loaded alginate poly-L-lysine microparticles in human volunteers. *Drug Deliv.* 14, 265-271.

539 Ding, W.K., Shah, N.P., 2009. Effect of various encapsulating materials on the stability of
540 probiotic bacteria. *J. Food Sci.* 74, M100-M107.

541 Doherty, S., Auty, M., Stanton, C., Ross, R., Fitzgerald, G., Brodkorb, A., 2012a. Application of
542 whey protein micro-bead coatings for enhanced strength and probiotic protection during fruit
543 juice storage and gastric incubation. *J. Microencapsulation*.

544 Doherty, S.B., Auty, M.A., Stanton, C., Ross, R.P., Fitzgerald, G.F., Brodkorb, A., 2012b. Survival
545 of entrapped *Lactobacillus rhamnosus* GG in whey protein micro-beads during simulated
546 ex vivo gastro-intestinal transit. *Int. Dairy J.* 22, 31-43.

547 El-Sherbiny, I.M., Abdel-Mogib, M., Dawidar, A.-A.M., Elsayed, A., Smyth, H.D.C., 2011.
548 Biodegradable pH-responsive alginate-poly (lactic-co-glycolic acid) nano/micro hydrogel
549 matrices for oral delivery of silymarin. *Carbohydr. Polym.* 83, 1345-1354.

550 Fuller, R., 1991. Probiotics in Human Medicine. *Gut* 32, 439-442.

551 Gibson, G.R., Probert, H.M., Loo, J.V., Rastall, R.A., Roberfroid, M.B., 2004. Dietary modulation
552 of the human colonic microbiota: updating the concept of prebiotics. *Nutr. Res. Rev.* 17, 259-
553 275.

554 Gibson, G.R., Roberfroid, M.B., 1995. Dietary Modulation of the Human Colonic Microbiota -
555 Introducing the Concept of Prebiotics. *J. Nutr.* 125, 1401-1412.

556 Graff, S., Hussain, S., Chaumeil, J.C., Charrueaul, C., 2008. Increased intestinal delivery of viable
557 *Saccharomyces boulardii* by encapsulation in microspheres. *Pharm. Res.* 25, 1290-1296.

558 Heidebach, T., Forst, P., Kulozik, U., 2009. Transglutaminase-induced caseinate gelation for the
559 microencapsulation of probiotic cells. *Int. Dairy J.* 19, 77-84.

560 Herrmann, J., Bodmeier, R., 1995. Somatostatin containing biodegradable microspheres
561 prepared by a modified solvent evaporation method based on W/O/W-multiple emulsions. *Int.*
562 *J. Pharm.* 126, 129-138.

563 Homayouni, A., Azizi, A., Ehsani, M.R., Yarmand, M.S., Razavi, S.H., 2008. Effect of
564 microencapsulation and resistant starch on the probiotic survival and sensory properties of
565 synbiotic ice cream. *Food Chem.* 111, 50-55.

566 Kawashima, Y., Niwa, T., Takeuchi, H., Hino, T., Itoh, Y., 1992. Hollow microspheres for use as a
567 floating controlled drug delivery system in the stomach. *J. Pharm. Sci.* 81, 135-140.

568 Klose, D., Siepmann, F., Elkharraz, K., Krenzlin, S., Siepmann, J., 2006. How porosity and size
569 affect the drug release mechanisms from PLGA-based microparticles. *Int. J. Pharm.* 314, 198-
570 206.

571 Krishnamachari, Y., Madan, P., Lin, S., 2007. Development of pH-and time-dependent oral
572 microparticles to optimize budesonide delivery to ileum and colon. *Int. J. Pharm.* 338, 238-247.

573 Lamprecht, A., Yamamoto, H., Takeuchi, H., Kawashima, Y., 2004. Design of pH-sensitive
574 microspheres for the colonic delivery of the immunosuppressive drug tacrolimus. *Eur. J.*
575 *Pharm. Biopharm.* 58, 37-43.

576 Li, X.Y., Chen, X.G., Cha, D.S., Park, H.J., Liu, C.S., 2009. Microencapsulation of a probiotic
577 bacteria with alginate-gelatin and its properties. *J. Microencapsulation* 26, 315-324.

578 Liserre, A.M., Re, M.I., Franco, B., 2007. Microencapsulation of *Bifidobacterium animalis* subsp
579 *lactis* in modified alginate-chitosan beads and evaluation of survival in simulated
580 gastrointestinal conditions. *Food Biotechnol.* 21, 1-16.

581 Mahboubian, A., Hashemein, S.K., Moghadam, S., Atyabi, F., Dinarvand, R., 2010. Preparation
582 and In-vitro Evaluation of Controlled Release PLGA Microparticles Containing Triptoreline. *Iran.*
583 *J. Pharm. Res.* 9, 369-378.

584 Mao, S., Xu, J., Cai, C., Germershaus, O., Shaper, A., Kissel, T., 2007. Effect of WOW process
585 parameters on morphology and burst release of FITC-dextran loaded PLGA microsphere. *Int. J.*
586 *Pharm.* 334, 137-148.

587 Mokarram, R.R., Mortazavi, S.A., Najafi, M.B.H., Shahidi, F., 2009. The influence of multi stage
588 alginate coating on survivability of potential probiotic bacteria in simulated gastric and
589 intestinal juice. *Food Res. Int.* 42, 1040-1045.

590 Muthukumarasamy, P., Allan-Wojtas, P., Holley, R.A., 2006. Stability of *Lactobacillus reuteri* in
591 different types of microcapsules. *J. Food Sci.* 71, M20-M24.

592 Ng, S.C., Hart, A.L., Kamm, M.A., Stagg, A.J., Knight, S.C., 2009. Mechanisms of action of
593 probiotics: recent advances. *Inflamm. Bowel Dis.* 15, 300-310.

594 Oliveira, A.C., Moretti, T.S., Boschini, C., Baliero, J.C.C., Freitas, O., Favaro-Trindade, C.S., 2007.
595 Stability of microencapsulated *B. lactis* (BI 01) and *L. acidophilus* (LAC 4) by complex
596 coacervation followed by spray drying. *J. Microencapsulation* 24, 673-681.

597 Rembacken, B.J., Snelling, A.M., Hawkey, P.M., Chalmers, D.M., Axon, A.T.R., 1999. Non-
598 pathogenic *Escherichia coli* versus mesalazine for the treatment of ulcerative colitis: a
599 randomised trial. *Lancet* 354, 635-639.

600 Schlicher, E.J.A.M., Postma, N.S., Zuidema, J., Talsma, H., Hennink, W.E., 1997. Preparation and
601 characterisation of Poly (d,l-lactic-co-glycolic acid) microspheres containing desferrioxamine.
602 *Int. J. Pharm.* 153, 235-245.

603 Schmidt, C., Lautenschlaeger, C., Collnot, E.M., Schumann, M., Bojarski, C., Schulzke, J.D., Lehr,
604 C.M., Stallmach, A., 2013. Nano- and microscaled particles for drug targeting to inflamed
605 intestinal mucosa: a first in vivo study in human patients. *J. Control. Release* 165, 139-145.

606 Searle, L.E., Best, A., Nunez, A., Salguero, F.J., Johnson, L., Weyer, U., Dugdale, A.H., Cooley,
607 W.A., Carter, B., Jones, G., Tzortzis, G., Woodward, M.J., La Razione, R.M., 2009. A mixture
608 containing galactooligosaccharide, produced by the enzymic activity of *Bifidobacterium*

609 bifidum, reduces Salmonella enterica serovar Typhimurium infection in mice. J. Med.
610 Microbiol. 58, 37-48.

611 Searle, L.E.J., Jones, G., Tzortzis, G., Woodward, M.J., Rastall, R.A., Gibson, G.R., La Ragione,
612 R.M., 2012. Low molecular weight fractions of BiMuno® exert immunostimulatory properties
613 in murine macrophages. Journal of Functional Foods 4, 941-953.

614 Sturesson, C., Carlfors, J., Edsman, K., Andersson, M., 1993. Preparation of biodegradable
615 poly(lactic-co-glycolic) acid microspheres and their in vitro release of timolol maleate. Int. J.
616 Pharm. 89, 235-244.

617 Sultana, K., Godward, G., Reynolds, N., Arumugaswamy, R., Peiris, P., Kailasapathy, K., 2000.
618 Encapsulation of probiotic bacteria with alginate-starch and evaluation of survival in simulated
619 gastrointestinal conditions and in yoghurt. Int. J. Food Microbiol. 62, 47-55.

620 Tzortzis, G., Goulas, A.K., Gee, J.M., Gibson, G.R., 2005. A novel galactooligosaccharide mixture
621 increases the bifidobacterial population numbers in a continuous in vitro fermentation system
622 and in the proximal colonic contents of pigs in vivo. J. Nutr. 135, 1726-1731.

623 Wichke, C., Schwendeman, S.P., 2008. Principles of encapsulating hydrophobic drugs in
624 PLA/PLGA microparticles. Int. J. Pharm. 364, 298-327.

625 Wright, B., Cave, R.A., Cook, J.P., Khutoryanskiy, V.V., Mi, S., Chen, B., Leyland, M., Connon,
626 C.J., 2012. Enhanced viability of corneal epithelial cells for efficient transport/storage using a
627 structurally modified calcium alginate hydrogel. Regen. Med. 7, 295-307.

628

629

630


631

632 **Supplementary information**

633

634 **Figure 1s.** GOS separation using ion-exchange chromatography. Peaks, from left to right:
635 penta-, tetra-, tri-, di- and mono- saccharides. RID: Refractive Index Detection

636

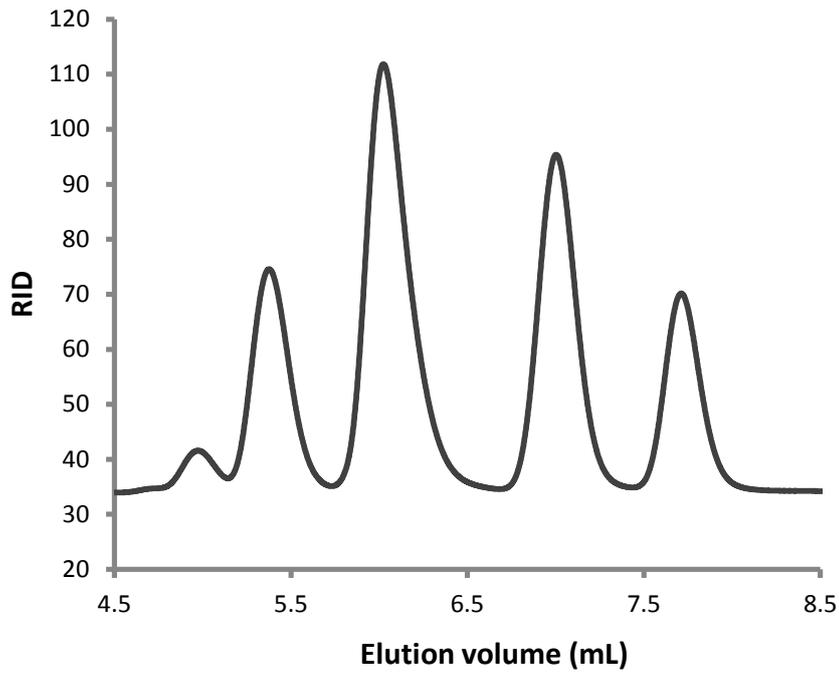

637

638

639 **Figure 2s.** *In vitro* GI passage used in GOS release studies

640

Region simulated	pH	Exposure time (h)
Stomach	2.0	0-1
Proximal small intestine	6.0	1-2
Distal small intestine	7.2	2-4
Large intestine	5.5	4 onwards

641

643 **Figure 3s.** Release of GOS from alginate and alginate-chitosan capsules

